



DR. THOGULUVA  
RAGHAVAN VIJAYARAM

FET Faculty (Engineering and Technology)  
MMU Multimedia University, Malaysia



# Hybrid Composite Castings



Liquid metallurgical processing of a new hybrid composite material containing tungsten carbide particulate and aluminium silicate particulate combined at different weight fraction percentage is discussed in this paper. Manufacturing of such hybrid composite has some advantages it is processed by near net shape techniques. Turbulence generated by the liquid metallurgical vortex mixing technique is the easiest technique for processing these hybrid composites. In this experimental work, aluminum-silicon alloy composites containing tungsten carbide and aluminium silicate combined particulate

combination of 2.5%, 5.0%, 7.5% and 10.0% on weight fraction basis are produced by using the liquid stirring method. These are processed in the form of slab castings containing 2.5%, 5%, 7.5% and 10% weight fraction of the two combination of particulate equally reinforced in LM6 alloy. A grey cast iron metallic mold is used to pour the hybrid composite slurry mixture. Mechanical, electrical and thermal properties are determined and all are discussed in this paper. The microstructures of the processed hybrid composites are captured to identify the presence of the two different reinforced particulates and its distribution uniformity.

Hybrid composites are usually used when a combination of properties of different types of particulates wants to be achieved, or when longitudinal as well as lateral mechanical performances are required [1,2]. Therefore, the development of aluminum matrix composites is receiving considerable emphasis in meeting the requirements of various industries. It has also reduced the thermal insulation requirements because of its lower thermal conductivity. Precision components in the missile guidance systems demands dimensional stability and the geometries of the components cannot change during usage [2]. Today's search is for composite materials with ever-higher service characteristics such as wear and heat resistance, high-temperature strength, antifriction, and cutting properties [3,4,5]. Particle shape has a major influence on processing characteristics [4, 5]. The shape is usually described in terms of the aspect ratio or shape factor [2]. Aspect ratio is the ratio of the largest dimension to the smallest dimension of the particle. This ratio ranges from unity, for a spherical particle to about 10 for flake like or needlelike particles. Shape factor or shape index of the particulate is a measure of the ratio of the surface area of the particle to its volume, normalized by reference to a spherical particle of equivalent volume [2]. The size distribution of particulates is an important consideration, because it affects the processing characteristics of the powder. Normally the fibers have a definite aspect ratio, which is defined by Length/Diameter ratio. Composite materials have found increasingly wider applications in aircraft, space vehicles, offshore structures, piping, electronic, automobiles, boats and sporting good. On a weight adjusted basis, many aluminium and aluminium alloy based composite materials can outperform the conventional ferrous and non-ferrous materials like cast iron, steel, aluminum, magnesium and virtually any other reinforced metal or alloy in a wide variety of applications [3]. Hence, probably, metal matrix composites will replace the conventional materials in many commercial and industrial applications in the near future. Special interest on particulate-reinforced metal matrix composites is due to the several merits offered by them. Researchers have reported that some composites exhibit a higher compressive strength than tensile strength due to the dominance of the presence of the reinforcement phase

since the compressive strength of the reinforcement particulate is very high. In the processing of metal matrix composite, one of the subjects of interest is to choose a suitable matrix and a reinforcement material. It influences the mechanical properties, shear modulus and shear strength and its processing characteristics. Reinforcement phase is the principal load-carrying member in a composite. Therefore, the orientation, of the reinforcement phase decides the properties of the composite. The reinforcing phase may be a particulate or a fiber, continuous type or discontinuous type. To improve the wettability with the liquid alloy or metal matrix material, the reinforcement phase is always preheated [4].

#### Materials and Methods

In this research, hybrid composite slab castings of dimension 190 mm\*30mm\*20mm & weighing approximately 302.10 grams are produced. A vortex stirrer is used to process the sample castings and it is shown below in Figure-1.

The processed hybrid composite castings are subjected to various testing to assess its mechanical properties, hardness, impact resistance and microstructure. Then electrical and thermal properties are determined and metallographic analysis has been performed to study the tungsten carbide particulate and aluminium silicate particulate distribution uniformity. Permanent grey cast iron metallic mold is used to pour 2.5%, 5%, 7.5% and 10% weight fraction of

Figure - 1 : Vortex Stirrer



combined tungsten carbide particulate and aluminium silicate particulate reinforced LM6 alloy hybrid composite slurry mixture to make hybrid composite slab castings. The mold material used in

this process is grey cast iron and it is reused to process more number of test castings. Testing for mechanical properties, thermal properties and electrical properties of the newly developed combined tungsten carbide particulate and aluminium silicate particulate reinforced aluminium-11.8 percentage silicon alloy matrix hybrid composites has been performed by using standard equipments and hence data are generated. Electrical resistivity and electrical conductivity values of the processed hybrid composites are calculated by finding the resistance in between the hybrid composite slab casting material. An indigenously designed circuit is used to determine the resistance value and hence the electrical conductivity and resistivity values are determined. Thermal diffusivity of the processed hybrid composites are measured by photo flash method and hence thermal conductivity values are determined. Metallographic analysis has been performed with the aid of a metallurgical microscope to study the tungsten carbide and aluminium silicate particulates distribution uniformity and hence to characterize the phases present in the processed new type of hybrid composites [6].

#### Results and Discussion

Results and data are obtained from the tested samples taken from the combined tungsten carbide and aluminium silicate particulate reinforced LM6 alloy slab composite castings made in grey cast iron mould. The values are reported for the mechanical, thermal and electrical properties as well as the density, hardness, impact strength and micro-structural features of the tungsten carbide and aluminium silicate particulate distribution for each weight fraction percentage addition to the LM6 alloy matrix. In this section, the above composites made in the grey cast iron are analyzed and the results are presented. It is found that the two combined tungsten carbide particulate and aluminium silicate particulate reinforced LM6 alloy matrix hybrid composite casting properties are superior to the LM6 alloy with and without grain refiner addition and no particulate reinforcement. In this innovative hybrid composite material development research work, the two combined particulates are reinforced in the alloy matrix are processed by liquid vortex metallurgical melt stirring technique. Microstructures of the processed hybrid composites based on the metallographic studies have

confirmed the uniformity of tungsten carbide particulate and aluminium silicate particulate distribution in the aluminium-11.8 % silicon alloy matrix. Sufficient amount of turbulence during the mixing of the particulates with the liquid alloy is necessary to get uniform particulate distribution during its solidification processing. The impeller blade type and its rotational speed have not shown any effect on the distribution uniformity. Nevertheless, faster pouring of the hybrid composite slurry mixture into the grey cast iron mold immediately after the mixing by vortex method has played a significant role in the distribution of the particulates used in this project. A small amount of tungsten particulate segregation has been observed due to its higher density. But, due to combination with aluminium silicate particulate, the effect of segregation is protected. In this section, the above composites made in the grey cast iron are analyzed and the results are presented in the corresponding graphs that are shown in Figure-2 to 8.

### Mechanical Properties

The tensile strength, yield stress and fracture stress values of combined tungsten carbide and aluminium silicate particulate composites are determined. The tensile strength of 10% and 2.5% weight fraction of the above combined particulate composite is 89.16 MPa and 173.63 MPa respectively. From this, it is clear that the tensile strength value decreases with the increase on the weight fraction % of combined tungsten carbide and aluminium silicate in the alloy matrix. The tensile strength value decreased gradually when above combination of particulate weight fraction addition of LM6 alloy matrix is increased and it is shown in the graph as Figure-2.

From the graph shown in Figure-3, it is observed that the values of specific strength gradually increase with an increased addition of combined particulate up to the addition of 7.5% weight fraction, after which the values start decreasing. Therefore, it is understood that the optimum value of adding the combined particulate to the alloy matrix is 7.5% by weight fraction. Data on the hardness of combined particulate reinforced composites made in grey cast iron mold is analyzed. It is found that the hardness value increases gradually with the increased addition % by weight and it is shown below in the graph as Figure-4. The maximum hardness value based Rockwell

Figure - 2 : Tensile Strength Vs Weight Fraction % Of Combined Tungsten Carbide and Aluminium Silicate


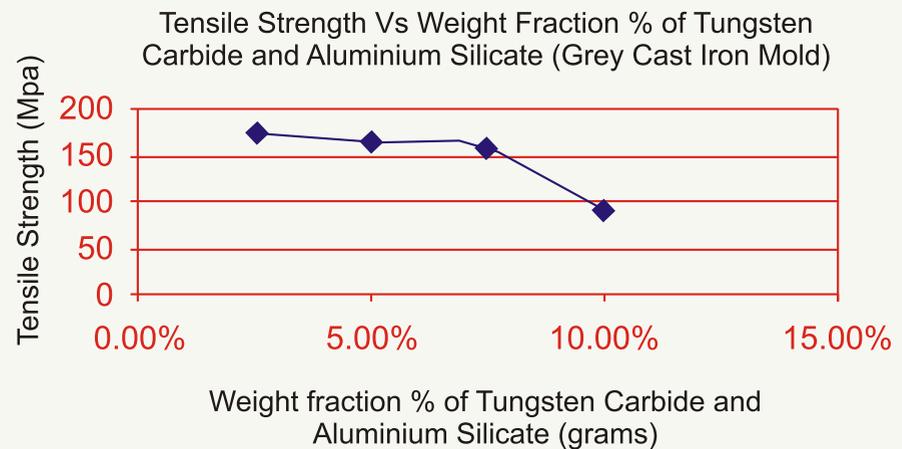


Figure - 3 : Specific Strength Vs Weight Fraction Percentage of Combined Tungsten Carbide and Aluminium Silicate

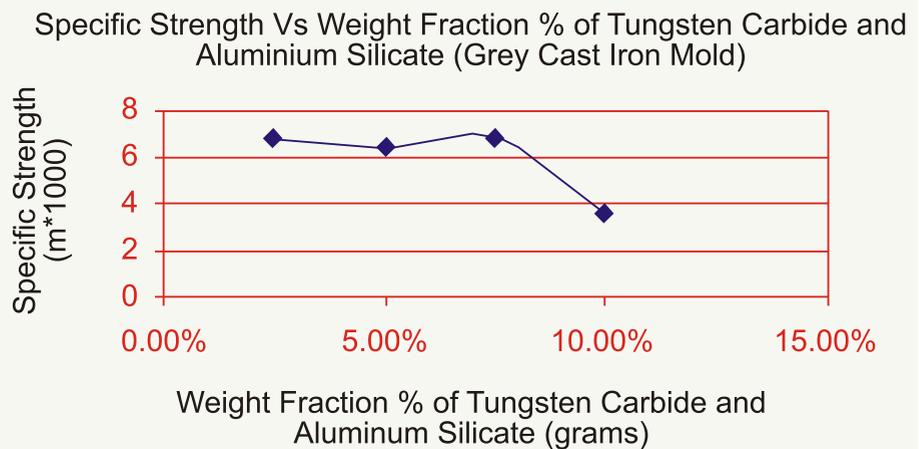

superficial 15N-S scale is 67.13 for 10% weight fraction addition.

The density values of the combined particulate composite castings poured grey cast iron mold is observed from the data. Based on the plotted graph as shown in Figure-5. It is found that there is no remarkable variation or changes observed in the determined density values of the processed combined particulate hybrid composite casting from the grey cast iron mold.

Impact strength values of the hybrid composite castings processed in grey cast iron mold is determined. From the analysis and plotted graphs, it is found that the impact strength values are gradually increasing up to a certain extent and then starts decreasing sharply, with the increasing addition of the two different particulates in the alloy matrix. Based on the plotted graph as shown in Figure-6, it is found that the optimum amount of tungsten carbide and

aluminium silicate to be added is nearly 5 % weight fraction and further addition is not effective in the impact strength improvement due to the reinforcement. The optimum value of impact strength is 8.838 N-m for 5% weight fraction addition of combined particulate to the alloy matrix.

### Electrical Properties

The processed hybrid composite castings made in grey cast iron metal mold are tested for electrical properties. Graph is plotted between the weight fraction % addition of combined particulate and electrical resistivity and it is shown in Figure-7. From the analysis, it is found that the electrical resistivities of the hybrid composites are decreased with the increased addition in the alloy matrix.

The average electrical resistivity value for 10 percentage weight fraction of combined particulate addition to the alloy matrix is 0.825765ohm-m and the

Figure - 4 : Hardness Vs Weight Fraction Percentage of Combined Tungsten Carbide and Aluminium Silicate

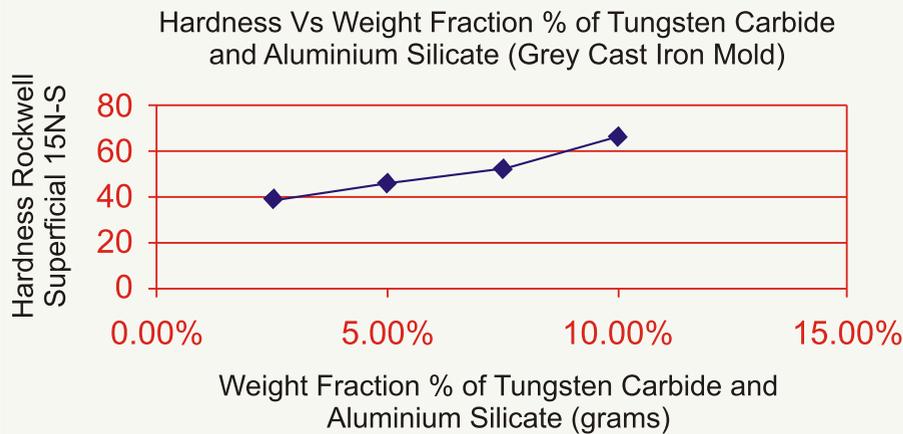


Figure - 5 : Density Vs Weight Fraction % of Combined Tungsten Carbide and Aluminium Silicate


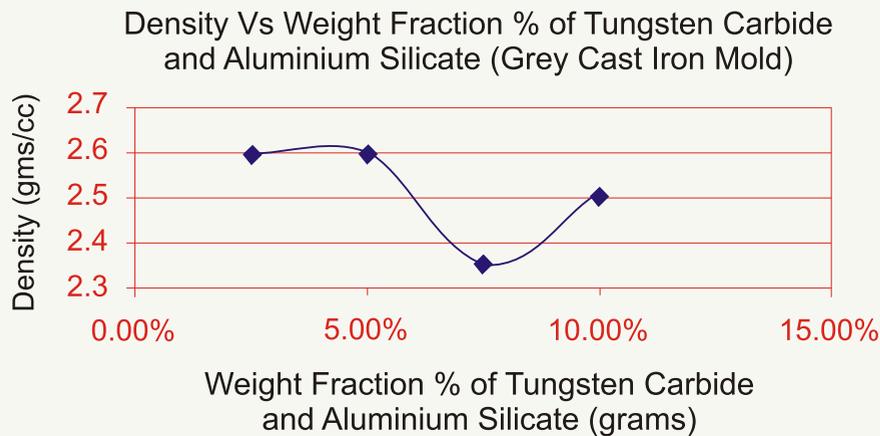


Figure - 6 : Impact Strength Vs Weight Fraction % of Combined Tungsten Carbide and Aluminium Silicate

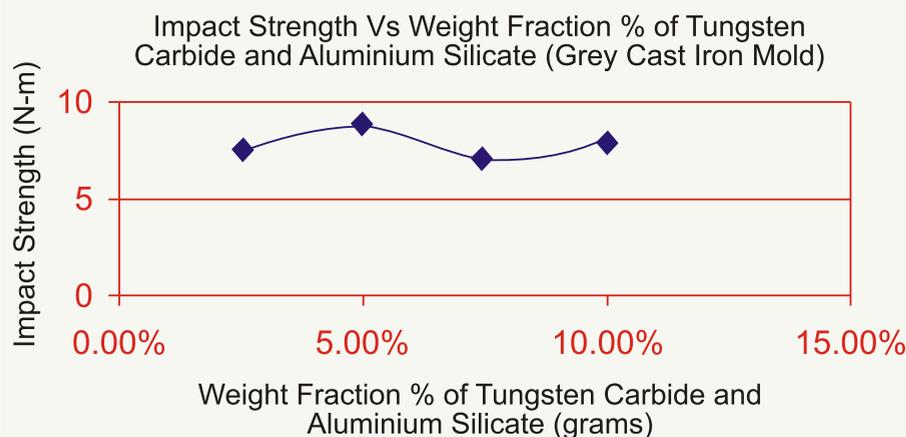

electrical conductivity value is 1.2124911/(ohm-m).

#### Thermal Properties

The processed combined hybrid composite castings made in grey cast iron

mold are tested for thermal properties. Graph is plotted for the weight fraction % addition of combined tungsten carbide and aluminium silicate particulate between thermal conductivity values. From the

analysis, it is found that the thermal conductivity of the combined composites is decreased with the increased addition of combined particulate in the alloy matrix. The data for thermal conductivity of grey cast iron mold is analyzed and this is illustrated in the plotted graph as shown in Figure-8. The thermal conductivity values for 10% weight fraction addition is 21.035 W/m K respectively.

Metallurgy of combined tungsten carbide and aluminium silicate particulate Reinforced aluminium-11.8% silicon alloy hybrid composites

Microstructural observation at different magnifications of the processed combined tungsten carbide and aluminium silicate particulate reinforced LM6 alloy composite test specimens made in grey cast iron mold are analyzed by a metallurgical microscope and hence it is employed to obtain some qualitative evidences on the combined tungsten carbide and aluminium silicate particulate distribution in the alloy matrix and bonding quality between the two particulates and the matrix. Metallographic samples of the combined composites are prepared under the standard procedures and HF, Hydrofluoric acid is used as an etchant to reveal the phases present in the LM6 alloy matrix. The samples are viewed at different magnifications such as at 50x, and 100x and photomicrographs are captured to predict the confirmation of the presence of the two particulates in the alloy matrix. Then, it is further studied to identify the particulate distribution. From the in-depth research on this, it is confirmed the presence and distribution of embedded two particulates in the matrix is uniform. The alloy matrix grains are finer and the bonding between particulate surface and the matrix material is satisfactory. It is found that, the morphological distribution of combined particulate for every weight fraction % addition increases. No interfacial reaction products are observed superficially. From this analysis, it is confirmed that the two different particulates reinforced LM6 alloy hybrid composite casting properties are superior to the LM6 alloy with and without grain refiner addition and no particulate reinforcement. In this section, a number of captured photomicrographs are shown in the Figure-9 to 11 for better understanding.

#### Conclusions

It is concluded that the two combined

Figure - 7 : Electrical Resistivity Vs Weight Fraction % of Combined Tungsten Carbide and Aluminium Silicate

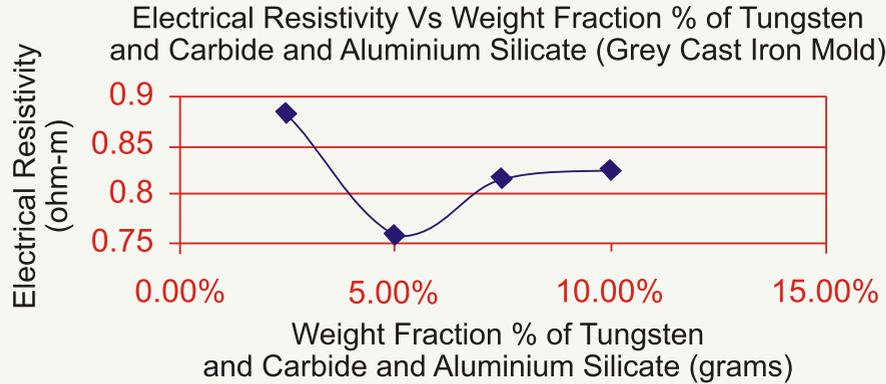


Figure - 8 : Thermal Conductivity Vs Weight Fraction Percentage of Combined Tungsten Carbide and Aluminium Silicate



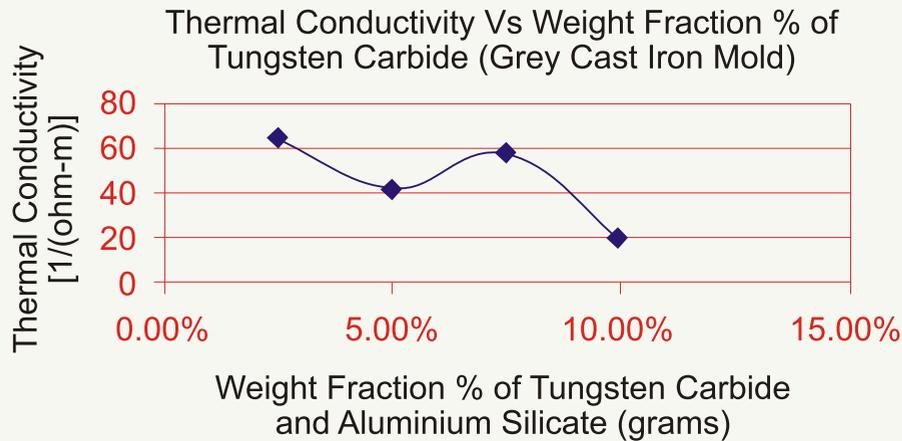


Figure - 9 : 2.5 % Tungsten Carbide and Aluminium Silicate Mixed Particulate Hybrid Composite Magnified at 50x

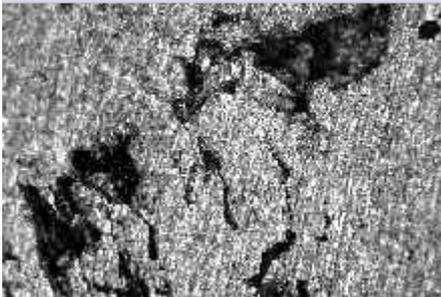


tungsten carbide particulate and aluminium silicate particulate reinforced LM6 alloy matrix hybrid composite casting properties are superior to the LM6 alloy with and without grain refiner addition and no particulate reinforcement. In this innovative hybrid composite material development research work, the two combined particulates are reinforced in the alloy matrix are processed by liquid vortex metallurgical melt stirring technique.

Figure - 10 : 5 % Tungsten Carbide & Aluminium Silicate Mixed Particulate Hybrid Composite Magnified at 50x

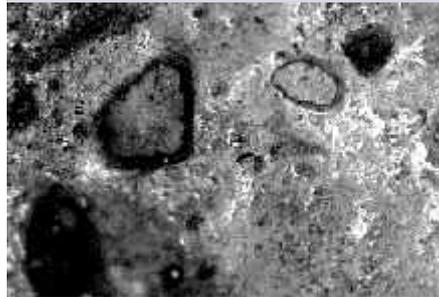

Microstructures of the processed hybrid composites based on the metallographic studies have confirmed the uniformity of tungsten carbide particulate and aluminium silicate particulate distribution in the aluminium-11.8% silicon alloy matrix. Sufficient amount of turbulence during the mixing of the particulates with the liquid alloy is necessary to get uniform particulate distribution during its solidification processing. The impeller blade type and its rotational speed have

Figure - 11 : 7.5 % Tungsten Carbide & Aluminium Silicate Mixed Particulate Hybrid Composite Magnified at 50x

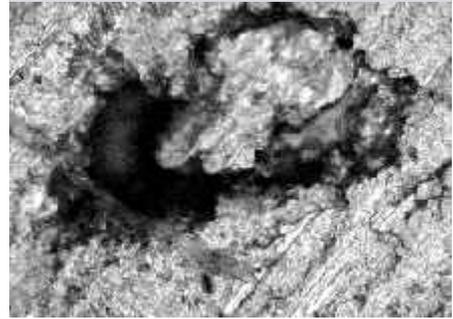

not shown any effect on the distribution uniformity. But, faster pouring of the hybrid composite slurry mixture into the grey cast iron mold immediately after the mixing by vortex method has played a significant role in the distribution of the particulates.. A small amount of tungsten particulate segregation has been observed due to its higher density. But, due to combination with aluminium silicate particulate, the effect of segregation is protected and future research work on this mentioned problem can be continued by a metallurgical engineering researcher.

#### Acknowledgement

The author expresses his thanks and gratitude to the Faculty of Engineering and Technology, FET, MMU, Multimedia University, Melaka Campus, Bukit Beruang, 75450, Melaka, Malaysia.

#### References

- (1) Aldrich Handbook of Fine Chemicals and Laboratory Equipment, The Sigma-Aldrich Family; 2004.
- (2) Arthur E. Hawkins, The shape of powder-particle outlines, Materials Science and Technology series, Research Studies Press Ltd, England, UK; 1993.
- (3) Doru .Michael .Stefanescu, Issues in liquid processing of particulate metal matrix composites, Key Engineering Materials, 1993; 79-80:75-90.
- (4) Donald F Adams, Leif A Carlson, R Byron Pipes, Experimental characterization of advanced composite materials, 3rd edition, CRC Press LLC, Florida, USA; 2003.
- (5) E.A.Feest, Metal Matrix Composites for Industrial Application, Materials & Design 1996; 7(2):58-64.
- (6) Thogulva Raghavan Vijayaram: Processing and properties studies of cast particulate reinforcedaluminium -11.8% silicon alloy based metal matrix composites, PhD Thesis in Mechanical Engineering, Faculty of Engineering, Universiti Putra Malaysia, UPM 43400 Serdang, Selangor Darul Ehsan, Malaysia 2003-2006.

○○○